

## Sn<sub>12</sub><sup>2-</sup>: Stannaspherene

Li-Feng Cui,<sup>†,‡</sup> Xin Huang,<sup>†,‡</sup> Lei-Ming Wang,<sup>†,‡</sup> Dmitry Yu. Zubarev,<sup>§</sup> Alexander I. Boldyrev,<sup>§</sup>  
Jun Li,<sup>‡</sup> and Lai-Sheng Wang<sup>\*,†,‡</sup>

Department of Physics, Washington State University, 2710 University Drive, Richland, Washington 99354, W. R.  
Wiley Environmental Molecular Sciences Laboratory and Chemical Sciences Division, Pacific Northwest National  
Laboratory, MS K8-88, Post Office Box 999, Richland, Washington 99352, and Department of Chemistry and  
Biochemistry, Utah State University, Logan, Utah 84322

Received March 24, 2006; E-mail: ls.wang@pnl.gov

During photoelectron spectroscopy (PES) experiments aimed at understanding the semiconductor-to-metal transition in tin clusters, the spectrum of Sn<sub>12</sub><sup>-</sup> was observed to be remarkably simple and totally different from the corresponding Ge<sub>12</sub><sup>-</sup> cluster, suggesting that Sn<sub>12</sub><sup>-</sup> is a unique and highly symmetric cluster. Structural optimization starting from an icosahedral (I<sub>h</sub>) cluster led to a slightly distorted cage with C<sub>5v</sub> symmetry. However, adding an electron to Sn<sub>12</sub><sup>-</sup> resulted in a stable closed-shell I<sub>h</sub>-Sn<sub>12</sub><sup>2-</sup> cluster, which was synthesized in the form of KSn<sub>12</sub><sup>-</sup> (K<sup>+</sup>[Sn<sub>12</sub><sup>2-</sup>]) with a similar PES spectrum as Sn<sub>12</sub><sup>-</sup>. The I<sub>h</sub>-Sn<sub>12</sub><sup>2-</sup> cage is shown to be bonded by four delocalized radial π bonds and nine delocalized on-sphere tangential σ bonds from the 5p orbitals of the Sn atoms, whereas the 5s<sup>2</sup> electrons remain largely localized and nonbonding. The bonding pattern in Sn<sub>12</sub><sup>2-</sup> is similar to the well-known B<sub>12</sub>H<sub>12</sub><sup>2-</sup> cage, with the twelve 5s<sup>2</sup> localized electron pairs replacing the twelve B–H bonds. The Sn<sub>12</sub><sup>2-</sup> cage has a diameter of 6.1 Å and can host most transition metal atoms in the periodic table.

The PES apparatus, featuring a laser vaporization supersonic cluster beam source and a magnetic bottle electron analyzer, has been described in detail previously.<sup>1</sup> A disk of pure tin was used as the laser vaporization target with a helium carrier gas. Negatively charged tin clusters (Sn<sub>x</sub><sup>-</sup>) were extracted from the cluster beam and were mass analyzed in a time-of-flight mass spectrometer. The cluster of interest was selected and then decelerated before being photodetached by a laser beam (193 nm from an excimer laser or 266 and 355 nm from a Nd:YAG laser). Photoelectrons were analyzed by the magnetic bottle time-of-flight analyzer and were calibrated by the known spectra of Cu<sup>-</sup> and Au<sup>-</sup>. The PES apparatus had an electron energy resolution of ΔE/E ~ 2.5%, that is, ~25 meV for 1 eV electrons.

Different from its lighter congeners, Si and Ge which are semiconductors, the normal allotrope of tin under ambient conditions (β-Sn) is a metal with a body-centered tetragonal lattice, but it also has a small band gap semiconducting phase (α-Sn) with a diamond lattice similar to Si and Ge that is stable at low temperatures.<sup>2</sup> Prior experimental<sup>3–7</sup> and theoretical<sup>8–11</sup> studies suggest that small tin clusters possess similar structures to those of Si and Ge. Small tin clusters were observed to exhibit melting temperatures exceeding that of the bulk,<sup>4</sup> consistent with the notion that small tin clusters have similar bonding configurations as those of the semiconductor Si and Ge clusters. Previous PES experiments<sup>12–14</sup> also suggested that the spectra of small Sn<sub>x</sub><sup>-</sup> clusters are similar to those of the corresponding Ge<sub>x</sub><sup>-</sup> clusters. However, these PES experiments were all done at low photon energies and under relatively low resolution.


In an effort to elucidate the semiconductor-to-metal transition as a function of size in tin clusters, we recently re-examined the PES of size-selected Sn<sub>x</sub><sup>-</sup> clusters with high photon energies (up to 6.424 eV or 193 nm) and under well-controlled experimental conditions. In the size range of x < 20, we indeed observed that the PES spectra of Sn<sub>x</sub><sup>-</sup> are similar to those of the corresponding Ge<sub>x</sub><sup>-</sup>, with the exception of Sn<sub>12</sub><sup>-</sup> (Figure S1). Whereas the spectrum of Ge<sub>12</sub><sup>-</sup> is rather congested with numerous poorly resolved features, that of Sn<sub>12</sub><sup>-</sup> is remarkably simple and well-structured (Figure 1a). Four bands were resolved in the binding energy range from 3 to 4 eV, followed by a large gap and two well-resolved bands around 5 eV. The lowest energy band yielded an adiabatic detachment energy, that is, the electron affinity of neutral Sn<sub>12</sub>, to be 3.23 ± 0.05 eV and a vertical detachment energy (VDE) of 3.34 ± 0.03 eV. Although low-symmetry structures similar to Ge<sub>12</sub> have been proposed for Sn<sub>12</sub>, the relatively simple and characteristic PES spectrum of Sn<sub>12</sub><sup>-</sup> immediately suggested that it should possess a high-symmetry structure different from that of Ge<sub>12</sub><sup>-</sup>.

In pondering the possible high-symmetry structures for Sn<sub>12</sub><sup>-</sup>, we started from the highest symmetry possible for a twelve-atom cluster, the icosahedral cage (for computational details, see Supporting Information). However, the Jahn–Teller effect led to a slightly lower symmetry C<sub>5v</sub> (<sup>2</sup>A<sub>1</sub>) species (Figure 2a), which is only slightly distorted from the I<sub>h</sub> structure, mainly by the depression of one apex atom. The computed first VDE (3.27 eV) of the C<sub>5v</sub> Sn<sub>12</sub><sup>-</sup> is in excellent agreement with the experimental value of 3.34 eV. By adding one electron to Sn<sub>12</sub><sup>-</sup>, we found that the resulting Sn<sub>12</sub><sup>2-</sup> species is a highly stable I<sub>h</sub> cage with a closed electron shell (Figure 2b and Figure S2).<sup>15</sup> Several other low-symmetry structures, including those suggested for Ge<sub>12</sub>, have also been calculated for Sn<sub>12</sub><sup>2-</sup>, but they are all much higher in energy (Figure S2). We were able to make Sn<sub>12</sub><sup>2-</sup> in the form of KSn<sub>12</sub><sup>-</sup> (K<sup>+</sup>[Sn<sub>12</sub><sup>2-</sup>]) experimentally by laser vaporization of a tin target containing ~15% K. The photoelectron spectrum of KSn<sub>12</sub><sup>-</sup> (Figure 1b) is very similar to that of Sn<sub>12</sub><sup>-</sup>, suggesting that the Sn<sub>12</sub><sup>2-</sup> motif is not distorted greatly due to the presence of K<sup>+</sup>. The ADE and VDE for the ground-state transition were measured as 2.99 ± 0.05 and 3.08 ± 0.03 eV, respectively, for KSn<sub>12</sub><sup>-</sup>. Our calculations showed that the K<sup>+</sup> counterion is outside the Sn<sub>12</sub><sup>2-</sup> cage with a C<sub>3v</sub> (<sup>1</sup>A<sub>1</sub>) symmetry (Figure 2c). Indeed, only relatively small structural perturbations were observed in the Sn<sub>12</sub><sup>2-</sup> cage as a result of the K<sup>+</sup> coordination. The isomer with K<sup>+</sup> inside the Sn<sub>12</sub><sup>2-</sup> cage is much higher in energy by 3.1 eV because of the large size of the K<sup>+</sup> ion, which expands the cage diameter from 6.07 Å (Figure 2b) to ~6.45 Å. We also calculated K coordinated to the two low-lying isomers of Sn<sub>12</sub><sup>-</sup>. We found they are both higher in energy and yield VDEs smaller than the experiment (Table S1). Only the


<sup>†</sup> Washington State University.

<sup>‡</sup> Pacific Northwest National Laboratory.

<sup>§</sup> Utah State University.

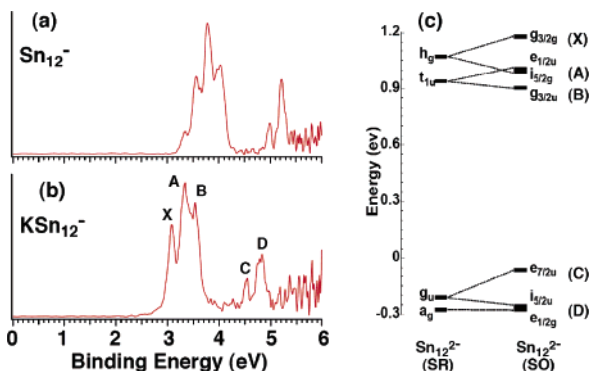

**Figure 1.** Photoelectron spectra of (a)  $\text{Sn}_{12}^-$  and (b)  $\text{KSn}_{12}^-$  at 193 nm. (c) Scalar relativistic (SR) energy levels of the 5p-based valence molecular orbitals of the  $I_h$   $\text{Sn}_{12}^{2-}$  and the correlation to the spin-orbit (SO) coupled levels of  $I_h^*$   $\text{Sn}_{12}^{2-}$ , where the asterisk indicates the double-group symmetry. See Supporting Information for computational details.

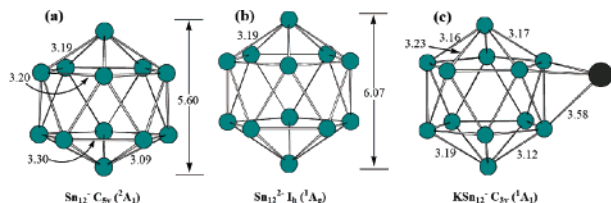

**Figure 2.** Optimized structures: (a)  $\text{Sn}_{12}^-$ ; (b)  $\text{Sn}_{12}^{2-}$ ; (c)  $\text{KSn}_{12}^-$ . The bond distances and cage diameters are in Å. See Supporting Information for computational details.

$\text{C}_{3v}$   $\text{KSn}_{12}^-$  (Figure 2c) yields a calculated VDE (3.0 eV) in good agreement with the experiment ( $3.08 \pm 0.03$  eV), lending considerable credence to the stability of the  $\text{Sn}_{12}^{2-}$  cage.

To help understand the chemical bonding in the  $I_h$ - $\text{Sn}_{12}^{2-}$  cage, we analyzed its valence molecular orbitals. Sn has a valence electron configuration of  $5s^25p^2$ . We found that because of the large energy separation between the 5s and 5p shells there is little s-p hybridization in  $\text{Sn}_{12}^{2-}$ . The  $5s^2$  electron pair is largely localized on each Sn atom, leaving only the two 5p electrons responsible for bonding on the  $\text{Sn}_{12}^{2-}$  cage. Figure 1c shows the valence molecular orbital diagram at the scalar relativistic (SR) and spin-orbit (SO) coupled levels. It is shown that the MO levels of  $\text{Sn}_{12}^{2-}$  with the SO effect are in excellent agreement with the PES spectral pattern of  $\text{K}^+[\text{Sn}_{12}^{2-}]$ ; the observed spectral features (X, A, B, C, D) are labeled in Figure 1c next to the SO levels.

Among the thirteen valence orbitals, four are delocalized radial  $\pi$ -bonding orbitals ( $a_g$  and  $t_{1u}$ ) formed from the radial  $p_z$  atomic orbitals. The remaining nine orbitals ( $g_u$  and  $h_g$ ) are delocalized in-sphere  $\sigma$ -bonding orbitals from the tangential  $p_x$  and  $p_y$  atomic orbitals (Figure S3a). The bonding pattern in  $\text{Sn}_{12}^{2-}$  is remarkably similar to that in the famous  $\text{B}_{12}\text{H}_{12}^{2-}$  molecule (Figure S3b), which was first predicted to be a stable molecule by molecular orbital theory<sup>16</sup> and subsequently synthesized.<sup>17</sup> The  $\text{B}_{12}$  cage in  $\text{B}_{12}\text{H}_{12}^{2-}$  is also bonded similarly by four delocalized radial  $\pi$ -bonding orbitals and nine in-sphere delocalized  $\sigma$  orbitals with 12 localized B-H bonds, which are equivalent to the  $5s^2$  electrons in the  $\text{Sn}_{12}^{2-}$  cage. Because of the delocalized  $\pi$  bonding in  $\text{Sn}_{12}^{2-}$  and its spherical symmetry, a name, stannaspherene, is suggested for this highly stable and symmetric cluster. In fact, our calculations suggest that the bare  $\text{Sn}_{12}^{2-}$  dianion is electronically stable with a 0.2 eV electron binding energy, more stable than  $\text{C}_{60}^{2-}$  or  $\text{C}_{70}^{2-}$ .<sup>18</sup>

Small polyhedral Sn clusters are known in inorganic complexes and the Zintl phases.<sup>19,20</sup> However, the  $I_h$ - $\text{Sn}_{12}^{2-}$  empty cage has not been known before. The high stability of this cluster suggests that it may be synthesized in the solid state using suitable ligands

or counterions. More excitingly, the  $\text{Sn}_{12}^{2-}$  cage has a diameter of  $\sim 6.1$  Å, only slightly smaller than that of  $\text{C}_{60}$ , and can host an atom inside much like the endohedral fullerenes. Indeed, theoretical calculations have shown that  $\text{Cd}@\text{Sn}_{12}$  is a stable  $I_h$  cage<sup>21</sup>, and several endohedral  $\text{Pb}_{12}$  clusters, such as  $\text{Al}@\text{Pb}_{12}^+$  and  $\text{Pt}@\text{Pb}_{12}^{2-}$ , have been synthesized.<sup>22-24</sup> A recent report revealed stable Cu-Sn cluster compositions from high-temperature annealing and suggested core-shell-type structures.<sup>25</sup> The stability of the stannaspherene and its large internal volume suggest that  $\text{Sn}_{12}^{2-}$  may trap many different types of atoms to form endohedral stannaspherenes.

**Acknowledgment.** This work was supported by NSF (DMR-0503383) and the John Simon Guggenheim Foundation and performed at EMSL, a national scientific user facility sponsored by DOE's Office of Biological and Environmental Research and located at the Pacific Northwest National Laboratory, operated for DOE by Battelle. Theoretical work done at Utah was supported by ACS-PRF (#43101-AC6) and NSF (CHE-0404937). The computations were partially performed using MSCF at EMSL.

**Supporting Information Available:** Theoretical details, the comparison of the photoelectron spectra of  $\text{Sn}_x^-$  and  $\text{Ge}_x^-$  ( $x = 11-13$ ), alternative structures for  $\text{Sn}_{12}^{2-}$ , and the comparison of the molecular orbital contours of  $\text{Sn}_{12}^{2-}$  and  $\text{B}_{12}\text{H}_{12}^{2-}$ . This material is available free of charge via the Internet at <http://pubs.acs.org>.

## References

- Wang, L. S.; Wu, H. In *Advances in Metal and Semiconductor Clusters. IV. Cluster Materials*; Duncan, M. A., Ed.; JAI Press: Greenwich, CT, 1998; pp 299-343.
- Burgers, W. G.; Groen, L. J. *Discuss. Faraday Soc.* **1957**, 23, 183.
- Shvartsburg, A. A.; Jarrold, M. F. *Phys. Rev. A: At., Mol., Opt. Phys.* **1999**, 60, 1235.
- Shvartsburg, A. A.; Jarrold, M. F. *Phys. Rev. Lett.* **2000**, 85, 2530.
- Martin, T. P.; Schaber, H. J. *Chem. Phys.* **1985**, 83, 855.
- LaiHing, K.; Wheeler, R. G.; Wilson, W. L.; Duncan, M. A. *J. Chem. Phys.* **1987**, 87, 3401.
- Yoshida, S.; Fuke, K. *J. Chem. Phys.* **1999**, 111, 3880.
- Lu, Z. Y.; Wang, C. Z.; Ho, K. M. *Phys. Rev. B: Condens. Matter* **2000**, 61, 2329.
- Majumder, C.; Kumar, V.; Mizuseki, H.; Kawazoe, Y. *Phys. Rev. B: Condens. Matter* **2001**, 64, 233405.
- Joshi, K.; Kanhere, D. G.; Blundell, S. A. *Phys. Rev. B: Condens. Matter* **2003**, 67, 235413.
- Chuang, F. C.; Wang, C. Z.; Ogut, S.; Chelikowsky, J. R.; Ho, K. M. *Phys. Rev. B: Condens. Matter* **2004**, 69, 165408.
- Gantefor, G.; Gausa, M.; Meiwes-Broer, K. H.; Lutz, H. O. *Z. Phys. D: At., Mol. Clusters* **1989**, 12, 405.
- Moravec, V. D.; Klopčic, S. A.; Jarrold, C. C. *J. Chem. Phys.* **1999**, 110, 5079.
- Negishi, Y.; Kawamata, H.; Nakajima, A.; Kaya, K. *J. Electron Spectrosc. Relat. Phenom.* **2000**, 106, 117.
- The lowest triplet state was calculated to be 34.7 kcal/mol higher at PW91/TZ2P, with spin-orbit coupling included.
- Longuet-Higgins, H. C.; Roberts, M. de V. *Proc. R. Soc. London, Ser. A* **1955**, 230, 110.
- Pitochelli, A. R.; Hawthorne, M. F. *J. Am. Chem. Soc.* **1960**, 82, 3228.
- Wang, X. B.; Woo, H. K.; Huang, X.; Kappes, M. M.; Wang, L. S.; *Phys. Rev. Lett.* **2006**, 96, 143002. Note that we could not produce the bare  $\text{Sn}_{12}^{2-}$  dianion in our laser vaporization experiment because of the coulomb repulsion between  $\text{Sn}_{12}^{2-}$  and an electron in the process of forming  $\text{Sn}_{12}^{2-}$ . It may be produced using electrospray once synthesized in solution, like that of  $\text{C}_{70}^{2-}$ .
- Wiberg, N.; Power, P. In *Molecular Clusters of the Main Group Elements*; Driess, M.; Noth, H., Eds.; Wiley-VCH Verlag: Weinheim, Germany, 2004; pp 188-208.
- Corbett, J. D. *Angew. Chem., Int. Ed.* **2000**, 39, 670.
- Kumar, V.; Kawazoe, Y. *Appl. Phys. Lett.* **2002**, 80, 859.
- Neukermans, S.; Janssens, E.; Chen, Z. F.; Silverans, R. E.; Schleyer, P. v. R.; Lievens, P. *Phys. Rev. Lett.* **2004**, 92, 163401.
- Esenturk, E. N.; Fetting, J.; Lam, Y. F.; Eichhorn, B. *Angew. Chem., Int. Ed.* **2004**, 43, 2132.
- Zhang, X.; Li, G.; Xing, X.; Zhao, X.; Tang, T.; Gao, Z. *Rapid Commun. Mass Spectrom.* **2001**, 15, 2399.
- Breaux, G. A.; Hillman, D. A.; Neal, C. M.; Jarrold, M. F. *J. Phys. Chem. A* **2005**, 109, 8755.

JA062052F