

A Heteroleptic Gold Hydride Nanocluster for Efficient and Selective Electrocatalytic Reduction of CO₂ to CO

Ze-Hua Gao, Kecheng Wei, Tao Wu, Jia Dong, De-en Jiang,* Shouheng Sun,* and Lai-Sheng Wang*

Cite This: *J. Am. Chem. Soc.* 2022, 144, 5258–5262

Read Online

ACCESS |



Metrics & More



Article Recommendations



Supporting Information

ABSTRACT: It has been a long-standing challenge to create and identify the active sites of heterogeneous catalysts, because it is difficult to precisely control the interfacial chemistry at the molecular level. Here we report the synthesis and catalysis of a heteroleptic gold trihydride nanocluster, $[\text{Au}_{22}\text{H}_3(\text{dppe})_3(\text{PPh}_3)_8]^{3+}$ [dppe = 1,2-bis(diphenylphosphino)ethane, PPh_3 = triphenylphosphine]. The Au_{22}H_3 core consists of two Au_{11} units bonded via six uncoordinated Au sites. The three H atoms bridge the six uncoordinated Au atoms and are found to play a key role in catalyzing electrochemical reduction of CO_2 to CO with a 92.7% Faradaic efficiency (FE) at -0.6 V (vs RHE) and high reaction activity (134 A/g_{Au} mass activity). The CO current density and FE_{CO} remained nearly constant for the CO_2 reduction reaction for more than 10 h, indicating remarkable stability of the Au_{22}H_3 catalyst. The Au_{22}H_3 catalytic performance is among the best Au-based catalysts reported thus far for electrochemical reduction of CO_2 . Density functional theory (DFT) calculations suggest that the hydride coordinated Au sites are the active centers, which facilitate the formation of the key $^*\text{COOH}$ intermediate.

Electrochemical CO_2 reduction reaction (CO_2RR) has been considered as a very promising strategy to convert CO_2 to value-added chemicals and to balance the carbon cycle.^{1,2} Gold-based nanomaterials have been one of the most widely studied catalysts for electrochemical conversion of CO_2 to CO with high selectivity and relatively low overpotentials.^{3,4} Despite the tremendous progress in producing monodisperse Au nanoparticles with appreciable activity and selectivity,^{5–9} their surface structure cannot be precisely resolved and well-defined, making it difficult to investigate the structure–activity relationship.^{10,11} Hence, it is highly desirable to achieve synthetic control in the coordination environments of surface Au atoms to create well-defined active centers for the elucidation of the structure–activity relationship of Au nanocatalysis.

In this quest, atomically precise Au nanoclusters have attracted intensive interest because they possess high molecular purity, well-defined structures, and high surface-to-volume ratios^{12–21} and have been studied as ideal model systems for understanding catalytic properties at the atomic level.^{22–25} In particular, a series of thiolate-protected Au nanoclusters have been studied for CO_2RR ,^{26–30} although the detailed catalytic mechanisms are not well understood and are controversial.^{28,31}


An ideal Au-nanocluster model catalyst should be atomically precise with uncoordinated Au ($uc\text{Au}$) sites serving as *in situ* catalytic active centers. Our focus has been on the Au_{20} pyramid, which is known to have all its atoms on the cluster surface.³² We have tried to synthesize the Au_{20} pyramid using different phosphine ligands with the hope of creating $uc\text{Au}$ sites with suitable ligands.^{33–35} The use of diphosphine ligands led to the synthesis of $\text{Au}_{22}(\text{dppo})_6$ [dppo = 1,8-bis(diphenylphosphino)octane], which was the first atom-precise Au nanocluster with 8 $uc\text{Au}$ sites³⁶ and was found to be able to catalyze the CO oxidation reaction under mild conditions,²² as

well as being a good catalyst for H_2 activation.³⁷ Further investigations led to the discovery of two Au nanohydride clusters with $uc\text{Au}$, $[\text{Au}_{22}\text{H}_4(\text{dppo})_6]^{2+}$ and $[\text{Au}_{22}\text{H}_3(\text{dppee})_7]^{3+}$ [dppee = bis(2-diphenylphosphino)ethyl ether], where the $uc\text{Au}$ sites are bridged by the H atoms.^{38,39} The steric effects produced by mixed bulky ligands^{40–43} provide another strategy to control the interfacial chemistry of Au nanoclusters to create catalytic active sites, which inspired us to consider mixing bidentate and monodentate phosphine ligands to try to synthesize the Au_{20} pyramid.

Here, we report the synthesis and catalysis of a new heteroleptic $[\text{Au}_{22}\text{H}_3(\text{dppe})_3(\text{PPh}_3)_8]^{3+}$ trihydride cluster [dppe = 1,2-bis(diphenylphosphino)ethane, PPh_3 = triphenyl phosphine], when we used a mixture of dppe and PPh_3 (Figure 1a). A combination of experimental and theoretical studies revealed that the Au_{22}H_3 core consists of two Au_{11} units that are bonded together via two triangular faces with the three H atoms bridging six $uc\text{Au}$ atoms at the interface. We have found that $[\text{Au}_{22}\text{H}_3(\text{dppe})_3(\text{PPh}_3)_8]^{3+}$ exhibits excellent performance for the selective electrocatalytic reduction of CO_2 to CO with a 92.7% Faradaic efficiency (FE) at -0.6 V [vs reversible hydrogen electrode (RHE)], high mass activity (134 A/g_{Au}), and high stability. The catalytic performance is among the best Au-based catalysts for electrochemical reduction of CO_2 to CO. The current study demonstrates the possibility of

Received: January 19, 2022

Published: March 15, 2022



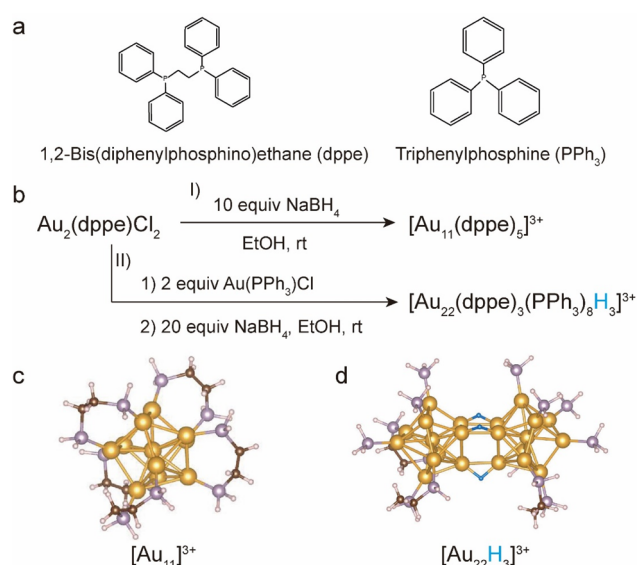


Figure 1. (a) Structures of dppe and PPh₃ ligands. (b) Synthetic routes toward (I) [Au₁₁(dppe)₅]³⁺ and (II) [Au₂₂(dppe)₃(PPh₃)₈H₃]³⁺. The DFT optimized structures of (c) [Au₁₁(dppe)₅]³⁺ and (d) [Au₂₂(dppe)₃(PPh₃)₈H₃]³⁺ clusters. Colors: Au = yellow; C = brown; P = purple; Hydride = blue; H on the ligands = white.

designing catalytically active centers using Au nanohydrides for potential applications.

The [Au₂₂H₃(dppe)₃(PPh₃)₈]³⁺ cluster (abbreviated as [Au₂₂H₃]³⁺ hereafter) was synthesized by reacting an excess amount of NaBH₄ with a mixture of Au₂(dppe)Cl₂ and Au(PPh₃)Cl precursors, as described in Figure 1b and the Supporting Information (SI). After purification, the final product showed a distinct peak in the electrospray ionization (ESI) mass spectrum (Figure 2a, top) due to [Au₂₂H₃]³⁺. To

ensure that the three H atoms on [Au₂₂H₃]³⁺ did not come from the ESI process, we used NaBD₄ instead of NaBH₄ to do the same reaction and obtained [Au₂₂D₃]³⁺ (Figure 2a, bottom). We further characterized [Au₂₂H₃]³⁺ using ¹H NMR and observed three peaks at 14.1 ppm (Figure 2b). The ratio of the integrated area for these hydride peaks to that of the 180 aromatic H atoms on the 11 phosphine ligands (6.6–7.9 ppm) is about 3:194. The observed chemical shift suggests that the three H atoms are directly bonded to Au, similar to those observed in previous Au–H nanoclusters: ~15.1 ppm in [Au₉H(PPh₃)₈]²⁺,⁴⁴ ~15.5 ppm in [Au₂₂H₄(dppo)₆]²⁺,³⁸ and ~15 ppm in [Au₂₂H₃(dppe)₇]³⁺.³⁹ The ³¹P NMR spectrum of the [Au₂₂H₃]³⁺ cluster, however, displayed multiple peaks in the range 45–60 ppm (Figure S1), suggesting the complexity of the phosphine environments.

By performing identical syntheses using Au₂(dppe)Cl₂ alone, the [Au₁₁(dppe)₅]³⁺ cluster [abbreviated as [Au₁₁]³⁺] was obtained (Figure 1b). The corresponding ESI mass spectrum and NMR spectra were also obtained, as shown in Figures S2–S4. The results show that the sample purity is high and the phosphine environments are similar on [Au₁₁]³⁺. We performed structural optimization using DFT calculations for both clusters. The optimized structures for [Au₁₁]³⁺ and [Au₂₂H₃]³⁺ are shown in Figure 1c and 1d, respectively. [Au₁₁]³⁺ is fully capped with diphosphine ligands. However, the three H atoms bridge the six *uc*Au sites in the [Au₂₂H₃]³⁺ cluster, whereas the remaining 14 surface Au atoms are coordinated by the phosphine ligands. We compared the Au–Au bond lengths between our DFT calculations and the experimental results of ([Au₁₁(dppp)₅]³⁺ and [Au₂₂(dppo)₆]²⁺), both agreeing well with the reported crystal data (Table S1). The [Au₁₁]³⁺ cluster also shares similar bond lengths as the Au₁₁ unit in the [Au₂₂H₃]³⁺ cluster. More interestingly, we compared the UV–vis absorption spectra of these two clusters with those of [Au₂₂H₃(dppe)₇]³⁺ and [Au₂₂H₄(dppo)₆]²⁺ (Figure 2c) and found that the two Au₂₂H₃ clusters share similar absorption features at around 323, 394, and 446 nm. The [Au₁₁]³⁺ cluster exhibits analogous features at around 324 and 400 nm. To interpret these absorption features, we simulated the optical absorption spectra of the [Au₂₂H₃]³⁺ and [Au₁₁]³⁺ clusters using time-dependent density functional theory (TD-DFT). Overall, good agreement between the experiment and the simulation has been found for both clusters (Figure S18a, 18b). For [Au₂₂H₃]³⁺, the 323 nm band involves many close excitations of Au d → sp (Table S2), the 394 nm band is assigned mainly to the HOMO–7 → LUMO+1 transition (Au d/s → sp excitation), and the 446 nm band is assigned to HOMO → LUMO+9 transition (Au sp → p excitation). The frontier orbitals of [Au₂₂H₃]³⁺ involved in the transitions all show features along the rod-shaped structure of the cluster (Figure S18c). For comparison, the 324 nm band of the [Au₁₁]³⁺ cluster also involves many close excitations of mainly Au d → p (Table S3), while its 400 nm band has just a few strong transitions (Au sp → sp). The ligands are more involved in the frontier orbitals of the [Au₁₁]³⁺ cluster (Figure S18d). The results indicate that the Au₂₂ core in [Au₂₂H₃]³⁺ may also be composed of two Au₁₁ units bonded via Au atoms and the Au₁₁ units may have similar structures with the [Au₁₁]³⁺ cluster.

The stability of a high purity [Au₂₂H₃]³⁺ sample in solid state was tested at ambient conditions. The UV–vis absorption spectra were measured and compared after six months (Figure 2d). The three main absorption features remain prominent

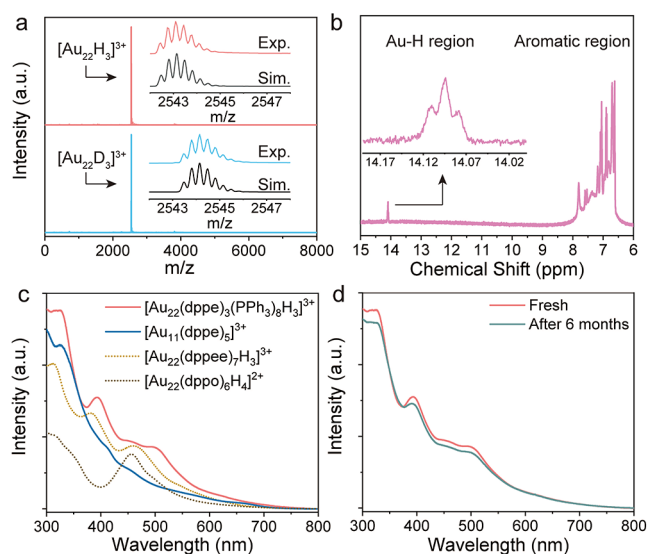


Figure 2. (a) ESI-MS spectra of [Au₂₂H₃]³⁺ and [Au₂₂D₃]³⁺; the insets show the experimental and simulated isotopic distributions. (b) The ¹H NMR spectrum of [Au₂₂H₃]³⁺; the inset shows the enlarged signal in the Au–H region. (c) Comparison of the UV–vis absorption spectra of [Au₂₂H₃]³⁺, [Au₁₁(dppe)₅]³⁺, [Au₂₂(dppe)₇H₃]³⁺, and [Au₂₂(dppo)₆H₄]²⁺. (d) UV–vis absorption spectra of [Au₂₂H₃]³⁺ solid sample stored for six months under ambient condition.

with only a slight decrease, suggesting the mixed ligand Au nanohydride cluster is very stable. The ESI mass spectra in Figure S5 also agree well with the absorption spectra, confirming its high stability in the solid state, even though the cluster is less stable in solution (Figure S8).

We studied the surface redox properties and CO₂RR activities of [Au₂₂H₃]³⁺, in comparison with those of [Au₁₁]³⁺. We first tested the cyclic voltammetry (CV) of the two clusters, as shown in Figure S9. It demonstrates that the existence of H atoms in the [Au₂₂H₃]³⁺ cluster leads to a unique oxidation peak at 0.88 V and shifts the Au(I)/Au(0) reduction peak from 1.02 to 1.05 V relative to [Au₁₁]³⁺. Figures S10 and S11 show the CVs of [Au₂₂H₃]³⁺ and [Au₁₁]³⁺ in N₂- and CO₂-saturated 0.5 M KHCO₃. The current density starts to increase as the potential reaches approximately −0.3 V in the N₂-saturated electrolyte, due to the hydrogen evolution reaction (HER) and CO₂RR. Both clusters have higher current densities in CO₂-saturated solution under the same potential, indicating both samples can effectively catalyze the electroreduction of CO₂. The electrocatalytic reduction of CO₂ was studied by linear sweep voltammetry (LSV) in the CO₂-saturated 0.5 M KHCO₃ (Figure 3a) to obtain the potentials required to reduce CO₂. The [Au₂₂H₃]³⁺ cluster shows a lower onset potential and higher current density relative to [Au₁₁]³⁺. In the subsequent electrolysis test at a constant potential, only H₂ and CO were detected in all our experiments (as described in the SI and Figure S12). Figure 3b compares the potential

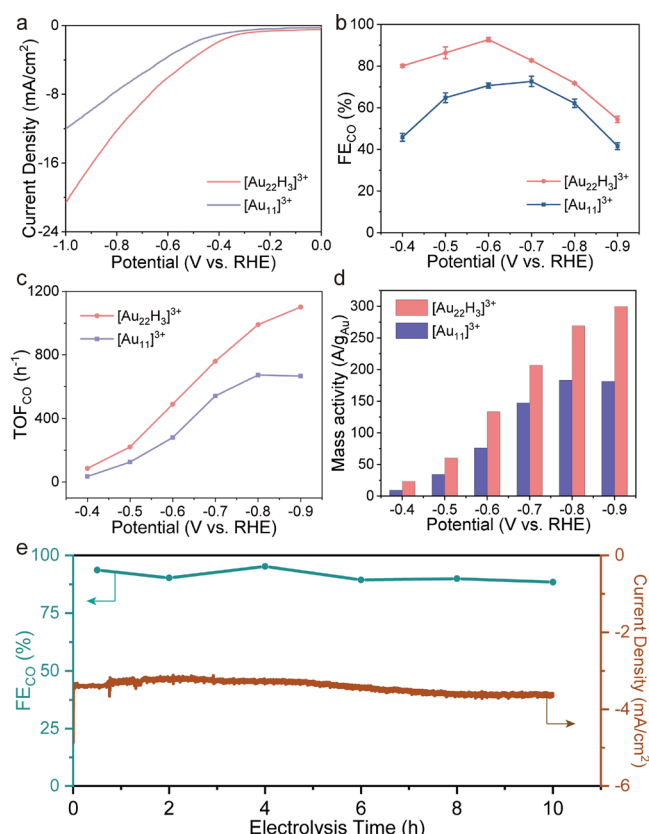


Figure 3. Selectivity, activity, and stability of [Au₂₂H₃]³⁺ and [Au₁₁]³⁺ in the electrocatalytic reduction of CO₂ to CO. (a) LSV curves. (b) FE_{CO} and (c) TOF_{CO} of the two clusters. (d) Potential-dependent mass activity of the two clusters. (e) Stability test of [Au₂₂H₃]³⁺ for electrolysis at −0.6 V.

dependent FEs for the formation of CO over [Au₂₂H₃]³⁺ and [Au₁₁]³⁺. We found that the [Au₂₂H₃]³⁺ cluster shows higher FE toward CO than the [Au₁₁]³⁺ cluster under all voltages. When more negative potentials are applied, the FE first increases and then decreases, reaching a maximum at about −0.6 V. This trend is similar to the recently reported phosphine/thiolate coprotected Au₅₅ cluster.⁴⁵ The best catalytic performance of [Au₂₂H₃]³⁺ was observed at −0.6 V with an FE_{CO} of 92.7%, which is significantly higher than that of the thiolate-protected Au₂₅ cluster at a similar potential.²⁷ Furthermore, the [Au₂₂H₃]³⁺ cluster also shows a very high turnover frequency (TOF) of 488 h^{−1} and mass activity of 134 A/g_{Au} at −0.6 V (Figure 3c and 3d), which is much higher than the values of Au nanoparticles^{6–9} at the same potential due to the higher ratio of surface atoms. For comparison, the [Au₁₁]³⁺ cluster has an FE_{CO} of 70.6% at −0.6 V, which is close to the reported value for [Au₁₁(PPh₃)₈Cl₂]⁺.⁴⁶ Relative to that of [Au₂₂H₃]³⁺, the current densities of [Au₁₁]³⁺ at all potentials are lower (Figure S13). In addition, the TOF value of 276 h^{−1} and mass activity of 75.8 A/g_{Au} at −0.6 V suggest a much lower activity of the [Au₁₁]³⁺ cluster than the [Au₂₂H₃]³⁺ cluster.

It is noteworthy that the [Au₂₂H₃]³⁺ cluster not only exhibits promising selectivity and activity toward CO₂RR but also remains stable during the electrochemical CO₂RR. The stability test results in Figure 3e indicate the current density stays steady at −3.5 mAcm^{−2} during the 10 h electrolysis at −0.6 V, with the FE_{CO} only dropping slightly (5.6%). It is also confirmed with XPS analysis before and after the electrolysis, as shown in Figure S17. The performance of the [Au₂₂H₃]³⁺ electrode was measured after one month of storage in air; the FE_{CO} at −0.6 V only drops 3.4% (Figure S16). All these results prove that the [Au₂₂H₃]³⁺ cluster is a stable CO₂RR catalyst.

DFT calculations were carried out to understand the mechanisms of the CO₂RR on [Au₂₂H₃]³⁺; the reaction pathways for the two nanoclusters are shown in Figure 4. We found that the bridge H atom in [Au₂₂H₃]³⁺ could directly

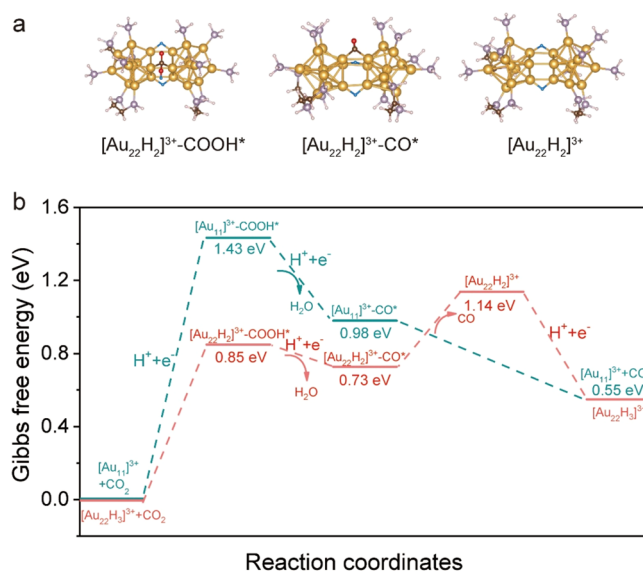


Figure 4. DFT structures and energetics of CO₂RR. (a) Optimized structures of the intermediates on [Au₂₂H₃]³⁺ for *COOH and *CO and after CO desorption. Color code: Au = yellow; C = brown; P = purple; Hydride = blue; H on the ligands = white; O = red. (b) Free energy profiles of CO₂RR on the [Au₁₁]³⁺ (cyan lines) and [Au₂₂H₃]³⁺ (red lines) clusters at 0 V vs RHE.

hydrogenate CO₂ to form adsorbed *COOH (Figure 4a) with a Gibbs free energy (ΔG) change of 0.85 eV (Figure 4b). Then, an electrochemical proton reduction process takes place on *COOH, leading to the formation of adsorbed CO* and H₂O. Although CO desorption has a higher barrier on [Au₂₂H₂]³⁺ than on [Au₁₁]³⁺, the formation of the key *COOH intermediate is much more difficult on [Au₁₁]³⁺ than on [Au₂₂H₂]³⁺. This is because the [Au₁₁]³⁺ cluster requires proton reduction from the electrolyte to form COOH* (Figure S19). As a result, the DFT profiles in Figure 4b indicate that it is much more favorable to form CO on [Au₂₂H₂]³⁺ than on [Au₁₁]³⁺, in agreement with our experimental observations (Figure 3). Moreover, Figure 4b shows that the H vacancy in [Au₂₂H₂]³⁺ can be readily recovered by proton reduction (Figure S20), completing the catalytic cycle. Although the CO₂RR pathway on [Au₂₂H₃]³⁺ shown in Figure 4b resembles the lattice hydride mechanism of CO₂RR on copper hydride nanoclusters,⁴⁷ an important difference is in selectivity, because HCOOH is preferred over CO on the latter. We have also computed the ΔG for HCOOH formation via hydride addition and the *HCOO intermediate on [Au₂₂H₂]³⁺ but found that it is less favorable than CO formation (Figure S21). In other words, the lattice hydrides in [Au₂₂H₃]³⁺ behave very differently from those in the Cu–H systems.

In conclusion, we have synthesized a new heteroleptic Au trihydride nanocluster, [Au₂₂H₃(dppe)₃(PPh₃)₈]³⁺. The use of the mixed ligands provides the cluster with both Au–H active sites and good stability. The cluster is found to be an excellent electrochemical CO₂RR catalyst, which exhibits high reactivity and selectivity to CO (92.7% FE and 134 A/g_{Au} mass activity at –0.6 V) and long-term stability. DFT studies of the CO₂RR mechanisms revealed that the Au nanohydride cluster facilitates the formation of the key *COOH intermediate, thereby favoring the CO product. The current work uncovers a unique Au nanohydride cluster with well-defined *in situ* catalytic centers for CO₂RR and suggests new approaches to design nanocatalysts for understanding structure–activity relationships and energy applications.

■ ASSOCIATED CONTENT

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/jacs.2c00725>.

Experimental methods, analyses of Au nanoclusters and their electrocatalysis, and computational details (PDF)

■ AUTHOR INFORMATION

Corresponding Authors

De-en Jiang – Department of Chemistry, University of California, Riverside, California 92521, United States;
✉ orcid.org/0000-0001-5167-0731; Email: djiang@ucr.edu

Shouheng Sun – Department of Chemistry, Brown University, Providence, Rhode Island 02912, United States;
✉ orcid.org/0000-0002-4051-0430;
Email: shouheng_sun@brown.edu

Lai-Sheng Wang – Department of Chemistry, Brown University, Providence, Rhode Island 02912, United States;
✉ orcid.org/0000-0003-1816-5738; Email: lai-sheng_wang@brown.edu

Authors

Ze-Hua Gao – Department of Chemistry, Brown University, Providence, Rhode Island 02912, United States
Kecheng Wei – Department of Chemistry, Brown University, Providence, Rhode Island 02912, United States
Tao Wu – Department of Chemistry, University of California, Riverside, California 92521, United States
Jia Dong – Department of Chemistry, Brown University, Providence, Rhode Island 02912, United States;
✉ orcid.org/0000-0001-7711-1655

Complete contact information is available at:
<https://pubs.acs.org/doi/10.1021/jacs.2c00725>

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

We thank Dr. T. L. Shen for help with the ESI-MS experiments and Dr. R. Hopson for help with the NMR experiments. This research was supported by a seed grant from the Office of the Vice President for Research at Brown University (to L.S.W.) and the NSF under Grant CHE-2102290 (to S.H.S.). The DFT computation was supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Chemical Sciences, Geosciences, and Biosciences Division, Catalysis Science Program (to D.E.J.).

■ REFERENCES

- (1) Turner, J. A. A Realizable Renewable Energy Future. *Science* **1999**, *285*, 687–689.
- (2) De Luna, P.; Hahn, C.; Higgins, D.; Jaffer, S. A.; Jaramillo, T. F.; Sargent, E. H. What Would It Take for Renewably Powered Electrosynthesis to Displace Petrochemical Processes? *Science* **2019**, *364*, 350.
- (3) Hori, Y.; Murata, A.; Kikuchi, K.; Suzuki, S. Electrochemical Reduction of Carbon Dioxides to Carbon Monoxide at a Gold Electrode in Aqueous Potassium Hydrogen Carbonate. *J. Chem. Soc., Chem. Commun.* **1987**, *10*, 728–729.
- (4) Wang, G.; Chen, J.; Ding, Y.; Cai, P.; Yi, L.; Li, Y.; Tu, C.; Hou, Y.; Wen, Z.; Dai, L. Electrocatalysis for CO₂ Conversion: From Fundamentals to Value-Added Products. *Chem. Soc. Rev.* **2021**, *50*, 4993–5061.
- (5) Haruta, M. Size-and Support-Dependency in the Catalysis of Gold. *Catal. Today* **1997**, *36*, 153–166.
- (6) Zhu, W.; Michalsky, R.; Metin, O.; Lv, H.; Guo, S.; Wright, C. J.; Sun, X.; Peterson, A. A.; Sun, S. Monodisperse Au Nanoparticles for Selective Electrocatalytic Reduction of CO₂ to CO. *J. Am. Chem. Soc.* **2013**, *135*, 16833–16836.
- (7) Mistry, H.; Reske, R.; Zeng, Z.; Zhao, Z. J.; Greeley, J.; Strasser, P.; Cuenya, B. R. Exceptional Size-Dependent Activity Enhancement in the Electroreduction of CO₂ over Au Nanoparticles. *J. Am. Chem. Soc.* **2014**, *136*, 16473–16476.
- (8) Zhu, W.; Zhang, Y. J.; Zhang, H.; Lv, H.; Li, Q.; Michalsky, R.; Peterson, A. A.; Sun, S. Active and Selective Conversion of CO₂ to CO on Ultrathin Au Nanowires. *J. Am. Chem. Soc.* **2014**, *136*, 16132–16135.
- (9) Souza, M. L.; Lima, F. H. Dibenzylthiocarbamate-Functionalized Small Gold Nanoparticles as Selective Catalysts for the Electrochemical Reduction of CO₂ to CO. *ACS Catal.* **2021**, *11*, 12208–12219.
- (10) Chakraborty, I.; Pradeep, T. Atomically Precise Clusters of Noble Metals: Emerging Link between Atoms and Nanoparticles. *Chem. Rev.* **2017**, *117*, 8208–8271.
- (11) Naveen, M. H.; Khan, R.; Bang, J. H. Gold Nanoclusters as Electrocatalysts: Atomic Level Understanding from Fundamentals to Applications. *Chem. Mater.* **2021**, *33*, 7595–7612.

- (12) Levi-Kalishman, Y.; Jadzinsky, P. D.; Kalisman, N.; Tsunoyama, H.; Tsukuda, T.; Bushnell, D. A.; Kornberg, R. D. Synthesis and Characterization of Au₁₀₂(p-MBA)₄₄ Nanoparticles. *J. Am. Chem. Soc.* **2011**, *133*, 2976–2982.
- (13) Li, G.; Jin, R. Atomically Precise Gold Nanoclusters as New Model Catalysts. *Acc. Chem. Res.* **2013**, *46*, 1749–1758.
- (14) Jin, R.; Zeng, C.; Zhou, M.; Chen, Y. Atomically Precise Colloidal Metal Nanoclusters and Nanoparticles: Fundamentals and Opportunities. *Chem. Rev.* **2016**, *116*, 10346–103413.
- (15) Yan, N.; Xia, N.; Liao, L.; Zhu, M.; Jin, F.; Jin, R.; Wu, Z. Unraveling the Long-Pursued Au₁₄₄ Structure by X-Ray Crystallography. *Sci. Adv.* **2018**, *4*, No. eaaf7259.
- (16) Zhu, M.; Aikens, C. M.; Hollander, F. J.; Schatz, G. C.; Jin, R. Correlating the Crystal Structure of a Thiol-Protected Au₂₅ cluster and Optical Properties. *J. Am. Chem. Soc.* **2008**, *130*, 5883–5885.
- (17) Negishi, Y.; Nakazaki, T.; Malola, S.; Takano, S.; Niihori, Y.; Kurashige, W.; Yamazoe, S.; Tsukuda, T.; Hakkinen, H. A Critical Size for Emergence of Nonbulk Electronic and Geometric Structures in Dodecanethiolate-Protected Au Clusters. *J. Am. Chem. Soc.* **2015**, *137*, 1206–1212.
- (18) Zeng, C.; Chen, Y.; Liu, C.; Nobusada, K.; Rosi, N. L.; Jin, R. Gold Tetrahedra Coil Up: Kekule-like and Double Helical Superstructures. *Sci. Adv.* **2015**, *1*, No. e1500425.
- (19) Konishi, K.; Iwasaki, M.; Shichibu, Y. Phosphine-Ligated Gold Clusters with Core+Exo Geometries: Unique Properties and Interactions at the Ligand-Cluster Interface. *Acc. Chem. Res.* **2018**, *51*, 3125–3133.
- (20) Yuan, S. F.; Xu, C. Q.; Li, J.; Wang, Q. M. A Ligand-Protected Golden Fullerene: The Dipyrityldiamido Au₃₂⁸⁺ Nanocluster. *Angew. Chem., Int. Ed.* **2019**, *58*, S906–S909.
- (21) Kang, X.; Wei, X.; Liu, X.; Wang, S.; Yao, T.; Wang, S.; Zhu, M. A Reasonable Approach for the Generation of Hollow Icosahedral Kernels in Metal Nanoclusters. *Nat. Commun.* **2021**, *12*, 6186.
- (22) Wu, Z.; Hu, G.; Jiang, D.-e.; Mullins, D. R.; Zhang, Q. F.; Allard, L. F., Jr.; Wang, L. S.; Overbury, S. H. Diphosphine-Protected Au₂₂ Nanoclusters on Oxide Supports Are Cctive for Gas-Phase Catalysis without Ligand Removal. *Nano Lett.* **2016**, *16*, 6560–6567.
- (23) Kwak, K.; Lee, D. Electrochemistry of Atomically Precise Metal Nanoclusters. *Acc. Chem. Res.* **2019**, *52*, 12–22.
- (24) Cai, X.; Hu, W.; Xu, S.; Yang, D.; Chen, M.; Shu, M.; Si, R.; Ding, W.; Zhu, Y. Structural Relaxation Enabled by Internal Vacancy Available in a 24-Atom Gold Cluster Reinforces Catalytic Reactivity. *J. Am. Chem. Soc.* **2020**, *142*, 4141–4153.
- (25) Hasegawa, S.; Takano, S.; Harano, K.; Tsukuda, T. New Magic Au₂₄ Cluster Stabilized by PVP: Selective Formation, Atomic Structure, and Oxidation Catalysis. *JACS Au* **2021**, *1*, 660–668.
- (26) Kauffman, D. R.; Alfonso, D.; Matranga, C.; Qian, H.; Jin, R. Experimental and Computational Investigation of Au₂₅ Clusters and CO₂: A Unique Interaction and Enhanced Electrocatalytic Activity. *J. Am. Chem. Soc.* **2012**, *134*, 10237–10243.
- (27) Zhao, S.; Austin, N.; Li, M.; Song, Y.; House, S. D.; Bernhard, S.; Yang, J. C.; Mpourmpakis, G.; Jin, R. Influence of Atomic-level Morphology on Catalysis: The Case of Sphere and Rod-like Gold Nanoclusters for CO₂ Electroreduction. *ACS Catal.* **2018**, *8*, 4996–5001.
- (28) Li, S.; Alfonso, D.; Nagarajan, A. V.; House, S. D.; Yang, J. C.; Kauffman, D. R.; Mpourmpakis, G.; Jin, R. Monopalladium Substitution in Gold Nanoclusters Enhances CO₂ Electroreduction Activity and Selectivity. *ACS Catal.* **2020**, *10*, 12011–12016.
- (29) Seong, H.; Efremov, V.; Park, G.; Kim, H.; Yoo, J. S.; Lee, D. Atomically Precise Gold Nanoclusters as Model Catalysts for Identifying Active Sites for Electroreduction of CO₂. *Angew. Chem., Int. Ed.* **2021**, *60*, 14563–14570.
- (30) Li, S.; Nagarajan, A. V.; Alfonso, D. R.; Sun, M.; Kauffman, D. R.; Mpourmpakis, G.; Jin, R. Boosting CO₂ Electrochemical Reduction with Atomically Precise Surface Modification on Gold Nanoclusters. *Angew. Chem., Int. Ed.* **2021**, *60*, 6351–6356.
- (31) Alfonso, D. R.; Kauffman, D.; Matranga, C. Active Sites of Ligand-Protected Au₂₅ Nanoparticle Catalysts for CO₂ Electroreduction to CO. *J. Chem. Phys.* **2016**, *144*, 184705.
- (32) Li, J.; Li, X.; Zhai, H. J.; Wang, L. S. Au₂₀: A Tetrahedral Cluster. *Science* **2003**, *299*, 864–867.
- (33) Zhang, H. F.; Stender, M.; Zhang, R.; Wang, C.; Li, J.; Wang, L. S. Toward the Solution Synthesis of the Tetrahedral Au₂₀ Cluster. *J. Phys. Chem. B* **2004**, *108*, 12259–12263.
- (34) Chen, J.; Zhang, Q. F.; Williard, P. G.; Wang, L. S. Synthesis and Structure Determination of a New Au₂₀ Nanocluster Protected by Tripodal Tetraphosphine Ligands. *Inorg. Chem.* **2014**, *53*, 3932–3934.
- (35) Zhang, Q.-F.; Chen, X.; Wang, L. S. Toward Solution Syntheses of the Tetrahedral Au₂₀ Pyramid and Atomically Precise Gold Nanoclusters with Uncoordinated Sites. *Acc. Chem. Res.* **2018**, *51*, 2159–2168.
- (36) Chen, J.; Zhang, Q. F.; Bonaccorso, T. A.; Williard, P. G.; Wang, L. S. Controlling Gold Nanoclusters by Diphosphine Ligands. *J. Am. Chem. Soc.* **2014**, *136*, 92–95.
- (37) Hu, G.; Wu, Z.; Jiang, D. E. Stronger-Than-Pt Hydrogen Adsorption in a Au₂₂ Nanocluster for the Hydrogen Evolution Reaction. *J. Mater. Chem. A* **2018**, *6*, 7532–7537.
- (38) Dong, J.; Gao, Z. H.; Zhang, Q. F.; Wang, L. S. The Synthesis, Bonding, and Transformation of a Ligand-Protected Gold Nanohydride Cluster. *Angew. Chem., Int. Ed.* **2021**, *60*, 2424–2430.
- (39) Dong, J.; Gao, Z. H.; Wang, L. S. The Synthesis and Characterization of a New Diphosphine-Protected Gold Hydride Nanocluster. *J. Chem. Phys.* **2021**, *155*, 034307.
- (40) de Silva, N.; Ha, J. M.; Solovyov, A.; Nigra, M. M.; Ogino, I.; Yeh, S. W.; Durkin, K. A.; Katz, A. A Bioinspired Approach for Controlling Accessibility in Calix[4]arene-bound Metal Cluster Catalysts. *Nat. Chem.* **2010**, *2*, 1062–1068.
- (41) Das, A.; Li, T.; Nobusada, K.; Zeng, Q.; Rosi, N. L.; Jin, R. Total Structure and Optical Properties of a Phosphine/Thiolate-Protected Au₂₄ Nanocluster. *J. Am. Chem. Soc.* **2012**, *134*, 20286–20289.
- (42) Yuan, S. F.; Lei, Z.; Guan, Z. J.; Wang, Q. M. Atomically Precise Preorganization of Open Metal Sites on Gold Nanoclusters with High Catalytic Performance. *Angew. Chem., Int. Ed.* **2021**, *60*, S225–S229.
- (43) Wang, X.; Wang, S.; Qian, S.; Liu, N.; Dou, X.; Yuan, X. Mechanistic Insights into the Two-phase Synthesis of Heteroleptic Au Nanoclusters. *Nanoscale* **2021**, *13*, 3512–3518.
- (44) Takano, S.; Hirai, H.; Muramatsu, S.; Tsukuda, T. Hydride-Doped Gold Superatom (Au₉H)²⁺: Synthesis, Structure, and Transformation. *J. Am. Chem. Soc.* **2018**, *140*, 8380–8383.
- (45) Wan, X. K.; Wang, J. Q.; Wang, Q. M. J. A. C. Ligand-Protected Au₅₅ with a Novel Structure and Remarkable CO₂ Electroreduction Performance. *Angew. Chem., Int. Ed.* **2021**, *60*, 20748–20753.
- (46) Narouz, M. R.; Osten, K. M.; Unsworth, P. J.; Man, R. W. Y.; Salorinne, K.; Takano, S.; Tomihara, R.; Kaappa, S.; Malola, S.; Dinh, C. T.; Padmos, J. D.; Ayoo, K.; Garrett, P. J.; Nambo, M.; Horton, J. H.; Sargent, E. H.; Hakkinen, H.; Tsukuda, T.; Crudden, C. M. N-Heterocyclic Carbene-Functionalized Magic Number Gold Nanoclusters. *Nat. Chem.* **2019**, *11*, 419–425.
- (47) Tang, Q.; Lee, Y.; Li, D. Y.; Choi, W.; Liu, C. W.; Lee, D.; Jiang, D. E. Lattice-hydride Mechanism in Electrocatalytic CO₂ Reduction by Structurally Precise Copper-Hydride Nanoclusters. *J. Am. Chem. Soc.* **2017**, *139*, 9728–9736.